

Impurity Site NMR Relaxation in Unconventional Superconductors

Masashige MATSUMOTO

Department of Physics, Faculty of Science, Shizuoka University, 836 Oya, Shizuoka 422-8529, Japan

(Received May 8, 2001)

Impurity nuclear spin relaxation is studied theoretically. A single impurity generates a bound state localized around the impurity atom in unconventional superconductors. With increasing impurity potential, the relaxation rate T_1^{-1} is reduced by the impurity potential. However, it has a peak at low temperatures due to the impurity bound state. The peak disappears at non-impurity sites. The impurity site NMR measurement detecting a local electronic structure just on the impurity atom is very useful for identifying the unconventional pairing states.

KEYWORDS: NMR, NQR, unconventional superconductivity, impurity

The study of unconventional superconductors has become one of the most attractive issues in recent condensed matter physics. These materials include heavy fermion compounds, high- T_c cuprates, organic superconductors and the recently discovered Sr_2RuO_4 . A great effort has been made to detect the unconventional superconductivity by several probes: specific heat measurement, tunneling spectroscopy, nuclear magnetic resonance (NMR), π -junction and so on. NMR experiments were important in the early stage of studying the unconventional superconductivity. It is well known that T_1^{-1} in s -wave superconductors has a Hebel-Slichter peak just below T_c , while it does not exhibit this feature in unconventional superconductors. On the other hand, it was also reported that the peak can be suppressed by the strong damping effect even for a s -wave state.¹⁾

To clarify this point, Ishida et al. performed a Cu site (bulk site) NMR experiment with Zn-doped $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ (YBCO).²⁾ They found that T_1^{-1} is proportional to T at low temperatures. Non-magnetic impurities do not break the s -wave superconductivity.³⁾ However, they break unconventional superconductivity and yield low-energy impurity states.^{4,5,6)} The observed T linear dependence of T_1^{-1} can therefore be understood as evidence of extended low-energy impurity states and supports an unconventional pairing state for YBCO. In this case, the effect of many impurities was important.

A single impurity can also break the unconventional superconductivity locally and generate a bound state around it.^{7,8,9)} Recently, Pan et al. observed such a low-energy state around a Zn atom in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ using a low-temperature scanning tunneling microscope (STM), showing a fourfold symmetrical structure which is consistent with a $d_{x^2-y^2}$ -wave pairing state.^{10,11)} Nishida et al. also observed the fourfold structure around a columnar defect by a STM.¹²⁾ At present, STM is the only instrument which can reveal the local electronic structure around a single impurity atom.

Usually, NMR is used to probe bulk electronic structure. For example, Cu site NMR measurements for high- T_c cuprates detect local electronic structure at the Cu

atom. Recently, impurity site NMR experiments were performed by several groups.^{13,14)} However, there is, so far, no theory for the impurity site NMR. The purposes of this paper are (1) to address the theory for the impurity site NMR and (2) to propose a new NMR experiment which probes the local quasiparticle states around a single impurity atom. In this study we concentrate our attentions on a single impurity problem, since we can solve it exactly. For unconventional superconductivity, we show that the impurity site NMR T_1^{-1} has a peak, while the peak disappears at the bulk site (non-impurity site). This peak at the impurity site is a common feature of all types of unconventional superconductors. The impurity site NMR can reveal the local quasiparticle structure as well, and provides us with a new experimental method for identifying unconventional superconductivity. Recently, NMR T_1^{-1} in a vortex state was studied theoretically.^{15,16)} They proposed that the NMR can be used as a site-selective probe by controlling the resonance frequency. Thus, NMR is gradually attracting attention as a local probe.

In the unconventional pairing case, the superconducting order parameter is suppressed around the impurity. However, we present our theory assuming a uniform order parameter, since we can capture the essential physics clearly without any complex analysis. Actually, we have performed numerical self-consistent calculations to include the spatial dependence of the order parameter. We have confirmed that the NMR T_1^{-1} has no qualitative difference between in the uniform and non-uniform order parameter cases. The most important point in the impurity site NMR is the existence of the impurity bound state, which does not depend on details of unconventional pairing states.

For the unconventional pairings, we focus on $p_x \pm ip_y$ -wave and $d_{x^2-y^2}$ -wave pairing states. The $p_x \pm ip_y$ -wave is the simplest and most essential symmetry suggested for the Sr_2RuO_4 superconductor.^{17,18,19)} This state is a spin triplet state and breaks the time-reversal symmetry.^{20,21)} For simplicity, we assume that the superconductor is basically two-dimensional and has a cylindrical

Fermi surface. The Matsubara Green function in a 2×2 matrix form is given by⁷⁾

$$\hat{G}(i\omega_m, \mathbf{r}, \mathbf{r}') = \hat{G}_0(i\omega_m, \mathbf{r}, \mathbf{r}') + \hat{G}_0(i\omega_m, \mathbf{r}, 0)U_0\hat{\tau}_3 \times \frac{1}{1 - \hat{G}_0(i\omega_m, 0, 0)U_0\hat{\tau}_3}\hat{G}_0(i\omega_m, 0, \mathbf{r}'), \quad (1)$$

where a single impurity is located at the origin of the coordinate. U_0 represents the strength of the short-range impurity potential. ω_m is the fermion Matsubara frequency and $\hat{\tau}_i$ ($i = 1, 2, 3$) represents the Pauli matrix in a charge space. For simplicity we use $\hbar = 1$ and $k_B = 1$ units throughout this letter. $\hat{G}_0$ is the non-perturbed ($U_0 = 0$) Green function given by

$$\hat{G}_0(i\omega_m, \mathbf{r}, \mathbf{r}') = -\frac{1}{\Omega} \sum_{\mathbf{k}} e^{i\mathbf{k} \cdot (\mathbf{r} - \mathbf{r}')} \frac{i\omega_m + \epsilon_{\mathbf{k}}\hat{\tau}_3 + \hat{\Delta}_{\mathbf{k}}}{\omega_m^2 + \epsilon_{\mathbf{k}}^2 + \hat{\Delta}_{\mathbf{k}}^2}. \quad (2)$$

Here, $\hat{\Delta}_{\mathbf{k}}$ is equal to $\Delta_{\mathbf{k}}\hat{\tau}_1$ and expresses the momentum-dependent order parameter. For the $p_x \pm ip_y$ -wave ($d_{x^2-y^2}$ -wave), $\Delta_{\mathbf{k}} = \Delta_p(T)e^{i\theta_{\mathbf{k}}}$ [$\Delta_{\mathbf{k}} = \Delta_d(T)\cos(2\theta_{\mathbf{k}})$]. Here, $\theta_{\mathbf{k}}$ is the angle of the Fermi wave vector measured from the k_x axis. We solve the gap equation in the bulk region and use the temperature-dependent order parameter $\Delta_p(T)$ ($\Delta_d(T)$) which is real and positive for the $p_x \pm ip_y$ -wave ($d_{x^2-y^2}$ -wave). $\epsilon_{\mathbf{k}}$ is the kinetic energy and Ω represents the volume of the system. NMR relaxation occurs via the hyperfine interaction between the nuclear spin and the conduction electrons. NMR T_1^{-1} at the impurity site is given in an explicit form²²⁾

$$T_1^{-1} = 2\pi\left(\frac{4\pi}{3}\right)^2(\gamma_e\gamma_n)^2W, \quad W = \int dE \frac{a_{11}(E)a_{22}(-E) - a_{12}(E)a_{21}(-E)}{1 + \cosh(E/T)}, \quad (3)$$

where W is proportional to the nuclear spin flip transition probability. γ_e and γ_n are the gyromagnetic ratios for the electron and nucleon, respectively. $a_{ij}(E) = -\text{Im}[G_{ij}(i\omega_m \rightarrow E + i\delta, 0, 0)]/\pi$, where the subscript of a_{ij} represents the matrix element of the Green function. Here, we have omitted the u_0 dependence in a_{ij} for simplicity, where $u_0 = \pi N_0 U_0$ (N_0 is the density of states per volume at the Fermi energy). δ is a positive, small number which expresses a finite level broadening.

In the s -wave case, NMR T_1^{-1} has the Hebel-Slichter peak just below T_c at the non-impurity site ($u_0 = 0$). At the impurity site ($u_0 \neq 0$), a_{ij} scales as $a_{ij}(E, u_0) = a_{ij}(E, 0)/(1 + u_0^2)$. The local density of states at the impurity is then simply reduced, keeping the same energy dependence. This is consistent with Anderson's theorem.³⁾ In the same manner, W scales as

$$W(u_0, T) = W(0, T)/(1 + u_0^2)^2. \quad (4)$$

Therefore, T_1^{-1} is simply reduced at the impurity site, while the temperature dependence does not change between the impurity site and the bulk site for the s -wave, as shown in Fig. 1(a).

For the $p_x \pm ip_y$ -wave, we show the results in Fig. 1(b). In this case, the temperature dependence at the impurity site is quite different from that of the bulk site. In the unconventional pairing case, both a_{12} and a_{21} are zero, since pair electrons cannot possess the same posi-

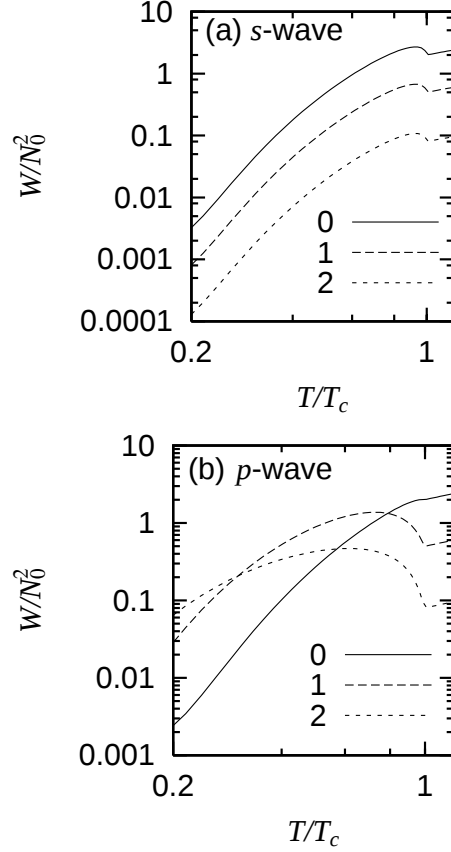


Fig. 1. Temperature dependence of W with various u_0 with a fixed damping rate $\delta/T_c = 0.1$. The number represents a value of u_0 . (a) and (b) are for the s -wave and $p_x \pm ip_y$ -wave, respectively. The peak of T_1^{-1} in (b) becomes higher with the decrease of δ/T_c [see eq. (7)]. The value of δ/T_c does not change the temperature dependence of T_1^{-1} .

tion. Therefore the coherence factor vanishes for unconventional pairings, resulting in the absence of the Hebel-Slichter peak. W is then expressed by the following simple form:

$$W = N_0^2 \int dE \frac{N_{\text{imp}}^2(E)}{1 + \cosh(E/T)}, \quad (5)$$

where $N_{\text{imp}}(E) = a_{11}(E)/N_0 = a_{22}(-E)/N_0$ is the dimensionless local density of states at the impurity atom. For the $p_x \pm ip_y$ -wave, a bound state appears around the single impurity. The energy position of the bound state is given by $E_B = -\text{sgn}(u_0)\Delta_p(T)/\sqrt{1 + u_0^2}$.²³⁾ In fact, an impurity effect is observed in Sr_2RuO_4 as a reduction of its T_c .²⁴⁾ N_{imp} in eq. (5) for the $p_x \pm ip_y$ -wave has the following analytic form:

$$N_{\text{imp}}(E) = \frac{N_p(E)}{1 + [u_0 N_p(E)]^2} \theta(|E| - \Delta_p(T)) + \frac{\pi |u_0| \Delta_p(T)}{(1 + u_0^2)^{3/2}} \delta(E - E_B), \quad (6)$$

where $N_p(E) = |E|/\sqrt{E^2 - \Delta_p^2(T)}$ is the dimensionless $p_x \pm ip_y$ -wave bulk density of states. θ and δ in eq. (6) are the Heaviside and δ -functions, respectively. The first and second terms in eq. (6) are the continuum and bound states, respectively. Introducing u_0 , we can see in

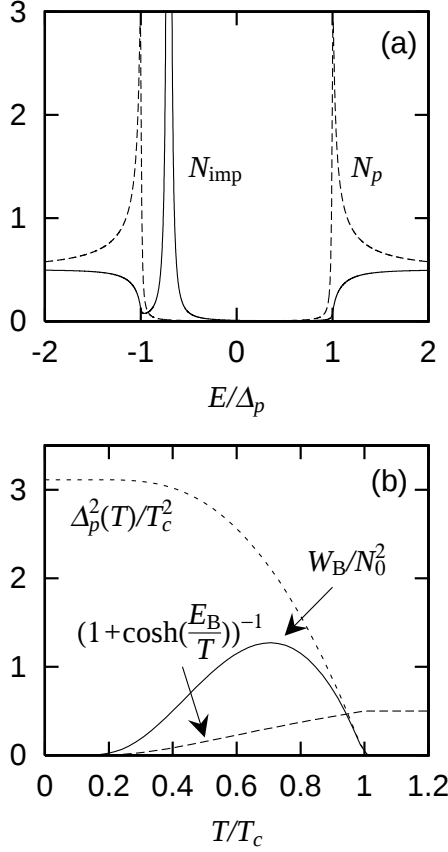


Fig. 2. (a) Dimensionless local density of states for the $p_x \pm ip_y$ -wave state. N_p is multiplied by $(1 + u_0^2)^{-1} = N_{\text{imp}}(\infty)$ for convenience. Parameters are chosen as $u_0 = 1$ and $\delta/\Delta_p = 0.01$. (b) Temperature dependence of W_B . Parameters are chosen as $u_0 = 1$ and $\delta/T_c = 0.1$.

Fig. 2(a) that the density of states from the quasiparticle continuum is decreased, while that of the impurity bound state increases. As in the s -wave case, W for the $p_x \pm ip_y$ -wave state is reduced with the increase of u_0 . However, as shown in Fig. 1(b), it drastically changes at low temperatures due to the impurity bound state. The bound state contribution to W behaves as

$$W_B \simeq N_0^2 \left[\frac{\Delta_p(T) u_0}{(1 + u_0^2)^{\frac{3}{2}}} \right]^2 \frac{\pi}{2\delta} [1 + \cosh(E_B/T)]^{-1}, \quad (7)$$

where $\delta(E - E_B) = (\delta/\pi)[(E - E_B)^2 + \delta^2]^{-1}$ has been used. Figure 2(b) clearly shows that W_B has a peak below T_c . Notice that the peak in W in Fig. 1(b) is closely related to the local impurity bound state. It is different from the Hebel-Slichter peak and can be distinguished, since T_1^{-1} does not exhibit such a peak at the bulk site for unconventional superconductivity. The peak appears only at the impurity site. At low temperatures, impurity nuclear spin relaxation occurs via the impurity bound state at the impurity site. As u_0 is increased, the peak position of W shifts to a lower temperature region [see Fig. 1(b)], which reflects the energy shift of the bound state. For a large u_0 , W_B can survive if δ is sufficiently small.

Next we study the $d_{x^2-y^2}$ -wave case, which is the most favorable pairing symmetry for high- T_c cuprates. In this

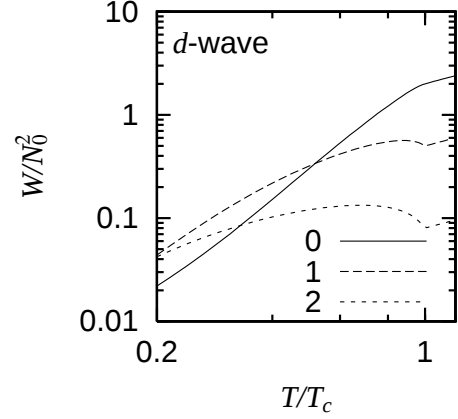


Fig. 3. Temperature dependence of W with various u_0 for the $d_{x^2-y^2}$ -wave with a fixed damping rate $\delta/T_c = 0.1$. The number represents a value of u_0 .

case, N_{imp} in eq. (5) takes the following form:

$$N_{\text{imp}}(E) = \frac{1}{u_0^2} \frac{N_d(E)}{[A(E) + 1/u_0]^2 + N_d^2(E)}, \quad (8)$$

where $A(E)$ and $N_d(E)$ are the real and imaginary parts of $\langle (E + i\delta)/\sqrt{(-iE + \delta)^2 + |\Delta_{\mathbf{k}}|^2} \rangle_{\text{FS}}$, respectively. Here, $\langle \cdots \rangle_{\text{FS}}$ represents an average over the Fermi surface. The energy position of the bound state is determined by the zero of $A(E) + 1/u_0$ and its effective broadening is $N_d(E)$ which is the dimensionless $d_{x^2-y^2}$ -wave bulk density of states. Similar to the $p_x \pm ip_y$ -wave case, the impurity site ($u_0 \neq 0$) NMR T_1^{-1} for the $d_{x^2-y^2}$ -wave has a peak due to the impurity bound state, as shown in Fig. 3.

The important point in this letter is that a single impurity generates a bound state in unconventional superconductors, and that the NMR experiment can detect the local impurity bound state by the impurity site T_1^{-1} measurement. We emphasize that the peak in T_1^{-1} at low temperatures in the impurity site NMR is a common feature exhibited by all types of unconventional superconductors. It does not depend on the details of unconventional pairing states. We have demonstrated this by examining the $p_x \pm ip_y$ -wave and $d_{x^2-y^2}$ -wave pairing states. The former is a fully gapped unconventional state, while the latter is a gapless one.

Recently Ishida et al. carried out NMR and NQR measurements on CeRu₂ with 1% Al (impurity) substitution for Ru.¹³⁾ They reported that the T_1^{-1} at the Al site was reduced to 10% of that of the Ru (bulk) site. The strength of the impurity scattering can be estimated as $|u_0| = 1.5$ by using eq. (4). If the pairing is unconventional, we can expect the appearance of a peak below T_c for $|u_0| = 1.5$, as shown in Figs. 1(b) and 3. However, the Al site T_1^{-1} does not exhibit such a peak. It is simply reduced, keeping the same exponential temperature dependence as that of the Ru site. This feature is consistent with our theory of impurity site NMR for the s -wave.

Very recently, Bobroff et al. succeeded in Li (impurity) site NMR measurement in YBCO with Li substituted for

Cu.¹⁴⁾ The Li concentrations of the samples were 0.85% and 1.86% per CuO₂ layer. For YBCO, Li induces a magnetic moment around it. Unfortunately, it is difficult to extract the contribution from the conduction electrons in T_1 , since the induced moment also generates the relaxation. However, this Li site experiment shows that the recent NMR experiment has enough sensitivity to detect T_1 at the impurity site in unconventional superconductors. The impurity concentration is about 1% for both CeRu₂ and YBCO. These experiments indicate that the impurity site NMR is possible at least for such impurity doping.

For the bulk site NMR T_1 measurement, it is important to observe whether the Hebel-Slichter peak is present or not. Examining the temperature dependence (exponential or power) at low temperatures is also important. (I) In the absence of the Hebel-Slichter peak, it is difficult to distinguish unconventional pairings from the s -wave for the bulk site measurement, since strong damping can suppress the coherence peak for the s -wave. (II) The temperature dependence of the bulk site T_1^{-1} is not useful for distinguishing fully gapped unconventional states from the s -wave. We cannot distinguish gapless unconventional states from the anisotropic s -wave, either. In contrast to the bulk site measurement, the impurity site measurement can distinguish for both (I) and (II) cases. The feature of unconventional pairings appears as a peak in T_1^{-1} only at the impurity site, while the peak disappears at the bulk site. On the other hand, for the s -wave, the temperature dependence of T_1^{-1} does not change for either impurity or bulk sites [see eq. (4) and Fig. 1(a)]. If we combine the two (bulk and impurity sites) NMR measurements, we can identify the unconventional pairing without ambiguity. Thus, the impurity site NMR is a powerful experimental method for probing unconventional superconductivity.

Our theory for a single impurity is applicable to a case with low impurity concentration. With the increase of the impurity concentration, extended impurity states are formed by the local impurity bound states, resulting in additional continuum energy levels below the energy gap. In this case, the impurity effect appears as a constant $T_1 T$ at low temperatures for both the impurity and bulk sites. However, the impurity site measurement is expected to exhibit the impurity effect more obviously than the bulk site, since the electronic states at the impurity site are strongly affected by the impurity atom. We note that the peak in T_1^{-1} of our theory for the single impurity (low impurity concentration) is much more drastic than the constant $T_1 T$, both of which are evidence of unconventional superconductivity.

The local electronic structure around the impurity atom reflects the superconducting pairing symmetry. So far, STM is the only probe of the local impurity state. However, STM experiments are strongly affected by the surface roughness. We note that the impurity site NMR can be used as a local probe regardless of annoying surface conditions.

In conclusion, we have addressed the theory for the impurity site NMR T_1^{-1} in unconventional superconductors. We have concentrated our attention on a single

impurity effect. There are two characteristic points of the impurity site NMR. The first one is that the relaxation rate T_1^{-1} is reduced by the impurity potential. The second is the peak in T_1^{-1} . It appears as direct result of the relaxation process via the impurity bound state. On the other hand, the peak vanishes at a non-impurity site. This is the remarkable difference in T_1^{-1} between the impurity site and non-impurity site NMR in unconventional superconductors. In contrast, the temperature dependence of T_1^{-1} does not change between the two sites for the conventional s -wave. Therefore, observation of the peak by the impurity site NMR measurement can provide strong evidence of an unconventional superconducting state.

The author expresses his sincere thanks to Y. Okuno and M. Sigrist for many discussions on the impurity effect in unconventional superconductors. He also thanks N. Hayashi and M. Takigawa for interesting discussions on NMR T_1^{-1} . He is grateful for the helpful discussions with H. Alloul and K. Ishida regarding NMR experiments. He would like to thank M. Koga for his helpful comments and critical reading of the manuscript. This work was supported by JSPS for Encouragement of Young Scientists (No. 10740169).

-
- [1] Y. Kitaoka et al.: *Physica C* **192** (1992) 272.
 - [2] K. Ishida et al.: *J. Phys. Soc. Jpn.* **62** (1993) 2803.
 - [3] P. W. Anderson: *J. Phys. Chem. Solids* **11** (1959) 26.
 - [4] P. J. Hirschfeld, D. Vollhardt and P. Wölfle: *Solid State Commun.* **59** (1986) 111; P. J. Hirschfeld, P. Wölfle and D. Einzel: *Phys. Rev. B* **37** (1988) 83; P. J. Hirschfeld and N. Goldenfeld: *Phys. Rev. B* **48** (1993) 4219.
 - [5] S. Schmitt-Rink, K. Miyake and C. M. Varma: *Phys. Rev. Lett.* **57** (1986) 2575.
 - [6] T. Hotta: *J. Phys. Soc. Jpn.* **62** (1993) 274.
 - [7] M. Matsumoto and H. Shiba: *J. Phys. Soc. Jpn.* **64** (1995) 1703.
 - [8] A. V. Balatsky, M. I. Salkola and A. Rosengren: *Phys. Rev. B* **51** (1995) 15547; M. I. Salkola, A. V. Balatsky and D. J. Scalapino: *Phys. Rev. Lett.* **77** (1996) 1841.
 - [9] Y. Onishi et al.: *J. Phys. Soc. Jpn.* **65** (1996) 675.
 - [10] S. H. Pan et al.: *Nature (London)* **403** (2000) 746.
 - [11] A. Yazdani et al.: *Phys. Rev. Lett.* **83** (1999) 176.
 - [12] N. Nishida et al.: *Physica B* **284-288** (2000) 967; M. Matsumoto, S. Kaneko and N. Nishida: *J. Phys. Soc. Jpn.* **66** (1998) 105.
 - [13] K. Ishida et al.: *Z. Naturforsch* **51 a** (1996) 793; H. Mukuda et al.: *J. Phys. Soc. Jpn.* **67** (1998) 2101.
 - [14] J. Bobroff et al.: *Phys. Rev. Lett.* **86** (2001) 4116.
 - [15] M. Takigawa, M. Ichioka and K. Machida: *Phys. Rev. Lett.* **83** (1999) 3057; M. Takigawa, M. Ichioka and K. Machida: *J. Phys. Soc. Jpn.* **69** 3943 (2000).
 - [16] D. K. Morr and R. Wortis: *Phys. Rev. B* **61** (2000) R882; R. Wortis, A. J. Berlinsky and C. Kallin: *Phys. Rev. B* **61** (2000) 12342; D. K. Morr: *Phys. Rev. B* **63** (2001) 214509.
 - [17] Y. Maeno et al.: *Nature (London)* **372** (1994) 532.
 - [18] T. M. Rice and M. Sigrist: *J. Phys.: Condens. Matter* **7** (1995) L643; T. M. Rice: *Nature (London)* **396** (1998) 627; M. Sigrist et al.: *Physica C* **317-318** (1999) 134.
 - [19] G. Baskaran: *Physica B* **223-224** (1996) 490.
 - [20] G. M. Luke et al.: *Nature (London)* **394** (1998) 558.
 - [21] K. Ishida et al.: *Nature (London)* **396** (1998) 658.
 - [22] R. Leadon and H. Suhl: *Phys. Rev.* **165** (1968) 596.
 - [23] Y. Okuno, M. Matsumoto and M. Sigrist: *J. Phys. Soc. Jpn.* **68** (1999) 3054.
 - [24] A. P. Mackenzie et al.: *Phys. Rev. Lett.* **80** (1998) 161.